

Metallic materials — Tube — Flanging test

The European Standard EN ISO 8494:2004 has the status of a
British Standard

ICS 77.040.10

National foreword

This British Standard is the official English language version of EN ISO 8494:2004. It is identical with ISO 8494:1998. It supersedes BS EN 10235:1994 which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee ISE/NFE/4, Mechanical testing of metals, to Subcommittee ISE/NFE/4/2, Ductility testing, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, page ii, pages 1 to 3 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 24 November 2004

© BSI 24 November 2004

ISBN 0 580 44842 8

English version

Metallic materials - Tube - Flanging test (ISO 8494:1998)

Matériaux métalliques - Tubes - Essai de rabatement de
collerette (ISO 8494:1998)

Metallische Werkstoffe - Rohr - Bördelversuch (ISO
8494:1998)

This European Standard was approved by CEN on 1 July 2004.

CEN members are bound to comply with the CEN/GENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Foreword

The text of ISO 8494:1998 has been prepared by Technical Committee ISO/TC 164 "Mechanical testing of metals" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 8494:2004 by Technical Committee EC/ISS/TC 29 "Steel tubes and fittings for steel tubes", the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

This document supersedes EN 10235:1993.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 8494:1998 has been approved by CEN as EN ISO 8494:2004 without any modifications.

INTERNATIONAL
STANDARD

ISO
8494

Second edition
1998-11-01

Metallic materials — Tube — Flanging test

Matériaux métalliques — Tubes — Essai de rabattement de collerette



Reference number
ISO 8494:1998(E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 8494 was prepared by Technical Committee ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

This second edition cancels and replaces the first edition (ISO 8494:1986), of which it constitutes a technical revision.

Metallic materials — Tube — Flanging test

1 Scope

This International Standard specifies a method for determining the ability of metallic tubes of circular cross-section to undergo plastic deformation during flange formation.

This International Standard is intended for tubes having an outside diameter no greater than 150 mm and a wall thickness no greater than 10 mm, although the range of diameters or wall thickness for which this International Standard is applicable may be more exactly specified in the relevant product standard.

2 Symbols, designations and units

Symbols, designations and units for the flanging test of tubes are given in table 1 and are shown in figure 1.

Table 1

Symbol	Designation	Unit
a^a	Wall thickness of the tube	mm
D	Original outside diameter of the tube	mm
D_u	Maximum outside diameter of the flange	mm
L	Length of the test piece before the test	mm
R	Corner radius of the flanging tool	mm
β	Angle of the conical mandrel	degree

^a The symbol T is also used in steel tube standards.

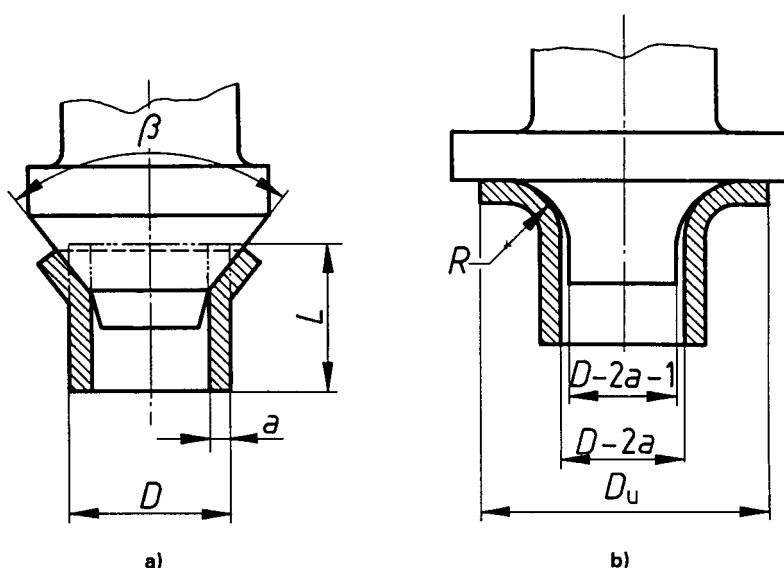


Figure 1

3 Principle

Forming of a flange on the end of a test piece cut from the tube, in a plane perpendicular to the axis of the tube, until the external diameter of the flange reaches the value specified in the relevant product standard.

4 Testing equipment

4.1 Variable-speed press or universal testing machine.

4.2 Forming equipment, made of polished material of sufficient hardness, consisting of

- a) a conical mandrel having a suitable angle (generally 90°);
- b) a flanging tool having
 - a cylindrical end of a diameter 1 mm less than the inside diameter of the tube;
 - a flat concentric portion, perpendicular to the axis of the flanging tool, and having a diameter no less than the required diameter of the flange;
- c) a supporting die, which may be used to support the tube during the formation of the flange.

5 Test piece

5.1 The length of the test piece shall be approximately $1,5 D$. The test piece may be shorter provided that the remaining cylindrical part of the test piece after flanging is at least $0,5 D$.

5.2 Both ends of the test piece shall be in the plane perpendicular to the axis of the tube. The edges of the end to be tested may be rounded by filing or chamfered by other methods.

NOTE — Non-rounded or non-chamfered edges are permissible if the test result meets the test requirements.

5.3 When welded tubes are subjected to the test, the internal welded flash may be removed.

6 Procedure

6.1 In general, the test shall be carried out at ambient temperature within the limits of 10 °C to 35 °C. The test carried out under controlled conditions shall be made at a temperature of $23\text{ °C} \pm 5\text{ °C}$.

6.2 Preform the test piece by forcing the conical mandrel into one end of the test piece until the diameter of the drifted test pieces is such that a flange having the specified diameter can be formed [see figure 1 a)].

6.3 Remove the conical mandrel and, if necessary, replace it with the flanging tool [see figure 1 b)].

6.4 Form the flange by applying axial force to the test piece until the drifted portion has formed a flange of the required diameter perpendicular to the axis of the test piece.

6.5 The conical mandrel may be lubricated. The conical mandrel shall not rotate relative to the test piece during the test.

6.6 In case of dispute, the rate of movement of the forming tools shall not exceed 50 mm/min.

6.7 The diameter of the flange and the radius R shall be as specified in the relevant product standard.

6.8 Interpretation of the flanging test shall be carried out in accordance with the requirements of the relevant product standard. When these requirements are not specified, the test piece shall be considered to have passed the

test if no cracks are visible without the use of magnifying aids. Slight cracking at the edges shall not be considered cause for rejection.

7 Test report

A test report shall be provided when so specified in the relevant product standard. In this case, the test report shall include at least the following information:

- a) reference to this International Standard, i.e. ISO 8494;
- b) identification of the test piece;
- c) dimensions of the test piece;
- d) maximum outside diameter of the expanded part of the test piece, D_u , or relative expansion as a percentage of the original diameter, D ;
- e) corner radius R of the flanging tool, when relevant;
- f) result of the test.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.